AD-A185 374   DECOMPOSITION OF METHANOL ACETALDEHYDE AND ACETONE ON   1/1
SUPPORTED RHODIUM CATALYSTS(U) AUBURN UNIV AL DEPT OF
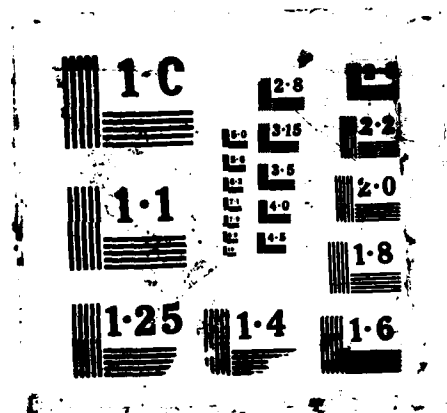CHEEISTRY   C H DAI ET AL. 10 SEP 87 TR-10
UNCLASSIFIED   N00014-83-K-0637   F/G 7/3   NL

AD-A185 374

DTIC FILE COPY (12)

OFFICE OF NAVAL RESEARCH

CONTRACT N00014-83-K-0637

TASK NO. NR 634-844

TECHNICAL REPORT NO. 10

DTIC
ELECTE
OCT 0 2 1987
S
D

DECOMPOSITION OF METHANOL, ACETALDEHYDE, AND ACETONE
ON SUPPORTED RHODIUM CATALYSTS

BY

C.H. Dai and S.D. Worley
Department of Chemistry
Auburn University
Auburn University, AL 36849

Sep. 18, 1987

AD-A185 374

REPORT DOCUMENTATION PAGE

1a. REPORT SECURITY CLASSIFICATION	1b. RESTRICTIVE MARKINGS
Unclassified	

2a. SECURITY CLASSIFICATION AUTHORITY	3. DISTRIBUTION/AVAILABILITY OF REPORT
2b. DECLASSIFICATION/DOWNGRADING SCHEDULE	Unlimited

4. PERFORMING ORGANIZATION REPORT NUMBER(S)	5. MONITORING ORGANIZATION REPORT NUMBER(S)
10	

6a. NAME OF PERFORMING ORGANIZATION	6b. OFFICE SYMBOL (If applicable)	7a. NAME OF MONITORING ORGANIZATION
Auburn University		Office of Naval Research

6c. ADDRESS (City, State and ZIP Code)	7b. ADDRESS (City, State and ZIP Code)
Department of Chemistry (Dr. S.D. Worley) Auburn University, AL 36849	800 N. Quincy St. Arlington, VA 22217

8a. NAME OF FUNDING/SPONSORING ORGANIZATION	8b. OFFICE SYMBOL (If applicable)	9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER
ONR	Code 413	N00014-83-K-0637

8c. ADDRESS (City, State and ZIP Code)	10. SOURCE OF FUNDING NOS.			
	PROGRAM ELEMENT NO.	PROJECT NO.	TASK NO.	WORK UNIT NO.
See 7b	NR 634-844			

11. TITLE (Include Security Classification) Decomposition of Methanol, Acetaldehyde, and Acetone on Supported Rhodium Catalysts

12. PERSONAL AUTHOR(S)
C.H. Dai and S.D. Worley*

13a. TYPE OF REPORT	13b. TIME COVERED	14. DATE OF REPORT (Yr., Mo., Day)	15. PAGE COUNT
Technical	FROM _____ TO _____	87 Sep 18	16

16. SUPPLEMENTARY NOTATION

To be published in Langmuir

17.	COSATI CODES		18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)
FIELD	GROUP	SUB. GR.	Infrared Spectroscopy, Decomposition, Methanol, Acetaldehyde, Acetone, Supported Rhodium

19. ABSTRACT (Continue on reverse if necessary and identify by block number)

The decomposition processes for methanol, acetaldehyde, and acetone over supported rhodium catalytic films have been investigated using infrared spectroscopy. An interesting support effect was observed for methanol decomposition with methane being the primary product over Rh/TiO_2 and dimethyl ether being formed over Rh/Al_2O_3. In the latter case the Al_2O_3 support was the active catalyst. For acetaldehyde decomposition the principle products were methane and acetone for both supported rhodium catalysts. Acetone decomposition produced only inactive carbon with no other infrared-detectable surface species. It is possible that a metallic rhodium gem dicarbonyl adsorbate was produced during the decomposition of acetaldehyde over Rh/Al_2O_3. Previous observations of the rhodium gem dicarbonyl species have referred to dispersed Rh^+ ions.

20. DISTRIBUTION/AVAILABILITY OF ABSTRACT	21. ABSTRACT SECURITY CLASSIFICATION
UNCLASSIFIED/UNLIMITED ☒ SAME AS RPT. ☐ DTIC USERS ☐	Unclassified

22a. NAME OF RESPONSIBLE INDIVIDUAL	22b. TELEPHONE NUMBER (Include Area Code)	22c. OFFICE SYMBOL
S.D. Worley	205-826-4043	

DD FORM 1473, 83 APR   EDITION OF 1 JAN 73 IS OBSOLETE.

Decomposition of Methanol, Acetaldehyde, and Acetone on Supported Rhodium
Catalysts

C.H. Dai and S.D. Worley*

Department of Chemistry, Auburn University, AL   36849

Accesion For		
NTIS CRA&I	☑	
DTIC TAB	☐	
Unannounced	☐	
Justification		
By		
Distribution /		
Availability Codes		
Dist	Avail and/or Special	
A-1		

Abstract

The decomposition processes for methanol, acetaldehyde, and acetone over supported rhodium catalytic films have been investigated using infrared spectroscopy. An interesting support effect was observed for methanol decomposition with methane being the primary product over Rh/TiO_2 and dimethyl ether being formed over Rh/Al_2O_3. In the latter case the Al_2O_3 support was the active catalyst. For acetaldehyde decomposition the principle products were methane and acetone for both supported rhodium catalysts. Acetone decomposition produced only inactive carbon with no other infrared-detectable surface species. It is possible that a metallic rhodium gem dicarbonyl adsorbate was produced during the decomposition of acetaldehyde over Rh/Al_2O_3. Previous observations of the rhodium gem dicarbonyl species have referred to dispersed Rh^+ ions.

Introduction

A considerable amount of work has been performed in these laboratories and elsewhere focused upon the elucidation of the mechanisms for the hydrogenation reactions of CO and CO_2 over supported rhodium catalysts.[1] The product distributions for these two reactions depend makedly upon the reaction conditions, with variables including (at least) temperature, pressure, nature of the support, and the presence or absence of alkali metal promotors. For example, a recent study of CO hydrogenation over Rh/TiO_2 showed that the presence of potassium ions poisoned the methanation reaction, but enhanced the yield of the oxygenated products acetaldehyde and acetone.[2] Our interest is currently directed toward the detection of intermediates in the hydrogenation reactions mentioned above using infrared spectroscopy as a primary analytical probe. We have been able to detect a rhodium carbonyl hydride species during the production of methane and higher hydrocarbons[1,3,4] in accord with the previous work of Solymosi and coworkers.[5-8] We now wish to extend our work to the detection of intermediates leading to the oxygenated products. The current paper will describe our observations concerning the reverse processes (decomposition of methanol, acetaldehyde, and acetone over supported rhodium catalyst films). The decomposition reactions of methanol over Rh(111)[9] and on the supports employed here[10-14] have been investigated previously, but not by using the infrared cell-reactor techniques employed in these laboratories.

Experimental Section

The catalytic sample preparation procedure developed here for Rh/TiO_2 and Rh/Al_2O_3 films has been described elsewhere[1-4] but will be reiterated briefly here. Slurries of $RhCl_3 \cdot 3H_2O$, support material (Degussa Titanium Dioxide P25, 50 m^2g^{-1} or Degussa Aluminum Oxide C, 100 m^2g^{-1}), in some cases KCl, and

water/acetone were sprayed from an atomizer onto a 25 mm CaF_2 infrared window held at $\underline{ca}$. 360 K. Evaporation of the solvents left a thin film ($\underline{ca}$. 4.3 mg cm^{-2}) of $RhCl_3 \cdot 3H_2O/TiO_2$ (or Al_2O_3), which in some runs contained potassium ions, adhered to the CaF_2 window. The window containing the catalytic film was mounted inside a Pyrex infrared cell reactor[1] which was then evacuated to 10^{-6} Torr using an ion pump. The sample was reduced by 85 Torr doses of hydrogen at 480 K for periods of 5, 5, 10, and 20 min, each reduction cycle being followed by evacuation. Prior studies in these laboratories and elsewhere have shown that this procedure provides a mixture of isolated Rh^+ ions and Rh^0 clusters; the Cl^- is lost as HCl. Following heating for 1 h at 490 K under vacuum, the samples were evacuated overnight to 10^{-6} Torr at ambient temperature. Then 20.0 Torr of either methanol, acetaldehyde, or acetone was introduced into the cell reactor. These materials had been purified by repetitive freeze-thaw evacuation cycles. After recording the infrared spectrum (Perkin-Elmer 983 with data system) at 300 K, the catalyst sample was brought to 440 K, and the infrared spectra were monitored as a function of time. Gaseous products were analyzed at the conclusion of the experiments using chromatography (Carle 400). Pressure measurements were made with an MKS Baratron capacitance manometer ($\pm$0.01 Torr). Runs involving support material only were made using the same general procedure.

Results and Discussion

Figures 1 and 2 show the infrared spectra for the methanol decomposition process over 2.2% Rh/TiO_2 and 2.2% Rh/Al_2O_3, respectively. A comparison of the analogous spectra in the two figures reveals that there was a significant support effect. Spectrum 1a shows that even at ambient temperature the Rh/TiO_2 film began to catalyze the decomposition of methanol, as some adsorbed

4

CO features were detected near 2000 cm^{-1} which overlap the C-O stretching overtone band[15] for CH$_3$OH (2035, P; 2056, Q; 2078, R). Heating for 1.5 h at 440 K (Fig. 1b) caused significant decomposition as evidenced by the declination of band intensity in the C-H stretch region (2850 and 2950 cm^{-1}) and the CO stretch region (1012, P; 1034, Q; 1060, R)[15], with a concomitant enhancement of the adsorbed CO bands in the range 1850-2120cm^{-1}. Based upon extensive prior work in these laboratories,[1,16,17] these bands can be assigned to CO stretching modes as follows: 1850, bridged dirhodium carbonyl; 1975, carbonyl bridged between Rh and the support TiO$_2$; 2037, the rhodium carbonyl hydride species; 2050, a "linear CO" rhodium species; 2120, CO adsorbed on Rh^{+2} (or at least in an oxidation state higher than +1)[16,18]. It is interesting that there was no evidence of sharp twin bands at 2030 and 2100 cm^{-1} indicating that the isolated Rh^{+1} "gem dicarbonyl" species was not formed during the decomposition of methanol. It is well known that CO gas causes disruption of Rh clusters to produce highly dispersed Rh^{+1} sites,[19,20] but evidently methanol is not capable of causing similar behavior. Figure 1c shows the result of further decomposition at 440 K (after 5.5 h); the bands attributed to methanol and CO surface species have greatly declined in intensity, and those present at 1304/3015 cm^{-1} and 2349 cm^{-1} indicate the formation of gas-phase methane and carbon dioxide. Analysis by gas chromatography indicated that at this point the gas-phase methanol was completely decomposed. Comparison with spectrum 1e indicates that under the same reaction conditions TiO$_2$ alone causes some decomposition of CH$_3$OH, but no CH$_4$, CO$_2$, or CO surface species were detected. It is clear that Rh plays an active role in the decomposition of CH$_3$OH when TiO$_2$ is the support. Spectrum 1d shows the result of adding potassium ions (K:Rh=1) to the 2.2% Rh/TiO$_2$ catalyst. This caused a substantial decrease in the rate of decomposition of

CH_3OH (86% decomposition indicated by GC), an elimination of CH_4 as a product, and a decline in the production of CO_2 and most adsorbed CO species. However, the bridged dirhodium carbonyl species was significantly enhanced. The increase of this CO species of Rh and the poisoning of the methanation reaction in the presence of potassium ions has been noted previously for the hydrogenation of CO and CO_2 over supported rhodium films.[2]

In contrast to the results noted for 2.2% Rh/TiO_2 above, for the 2.2% Rh/Al_2O_3 catalyst only the rhodium carbonyl hydride and bridged dirhodium carbonyl adsorbed CO species were produced in significant amounts (Fig. 2b, c), no decomposition occurred at 300 K, CH_4 and CO_2 were not produced in significant amounts, and the primary decomposition product was dimethyl ether (bands at 1180 and 1110 cm^{-1}, verified by gas chromatography). However, a comparison of spectra 2c and 2e indicates that the dimethyl ether production is catalyzed primarily by the Al_2O_3 support rather than by rhodium. Spectrum 2d shows that the presence of potassium ions poisons the production of dimethyl ether indicating that the K^+ is spread over the support as well as on Rh. The K^+ ions must also interact with Rh because the carbonyl hydride species was diminished, and the bridged dirhodium carbonyl species was enhanced when potassium was present. We would postulate that the potassium poisons the active Rh methanation sites by aiding the formation of inactive carbon on these sites and enhancing the formation of the bridged dirhodium carbonyl species, which we have noted before does not yield methane under the conditions (440 K and low pressure) of our experiments.[2] As noted before, the potassium ions also poison the production of dimethyl ether on the Al_2O_3 support. This is probably a result of blockage of Lewis acid sites, as pointed out by Busca et al. in their studies of the interaction of methanol with KOH doped TiO_2.[14]

Thus it might be postulated that under the conditions of our experiments, Rh/TiO_2 catalyzes the rupture of the C-O bond in methanol to produce active carbon (CH_3) which subsequently leads to CH_4 and CO_2, as products, while Rh/Al_2O_3 assists the rupture of the O-H bond in methanol as well to form CH_3O which subsequently leads to the production of dimethyl ether. In the latter case the Rh performs little useful purpose with the Al_2O_3 providing the catalysis.

Figures 3 and 4 present the infrared spectra for the decomposition of acetaldehyde over 2.2% Rh/TiO_2 and 2.2% Rh/Al_2O_3, respectively. In this case the results were similar for the two different supported catalysts. Spectrum 3a indicates that little acetaldehyde decomposed at 300 K, but upon heating at 440 K (spectra 3b,c), marked decomposition occurred (85% as measured by GC) to form CH_4 (1304 cm^{-1}), CO_2 (2349 cm^{-1}), CO (2143 cm^{-1}), adsorbed bridged rhodium carbonyl species (1800-2000 cm^{-1}), surface carbonate and acetate species (1410, 1445, 1526, 1576 cm^{-1}), and acetone (1240, 1340 cm^{-1}). Decomposition occurred over the pure TiO_2 support material also (Fig. 3e), but only surface acetate bands were observed. Thus it can be concluded that the acetate species was confined primarily to the TiO_2 support. It should be noted that Orita et al. have detected adsorbed acetate ions during the formation of acetaldehyde from the hydrogenation of CO over Rh/SiO_2.[21] Prior work in these laboratories suggested that acetaldehyde and acetone were produced from the bridged dirhodium carbonyl species during the hydrogenation of CO over 2.2% Rh/TiO_2, while methane was produced from the other adsorbed CO species.[2] Spectrum 3c shows that the only adsorbed CO/Rh species produced during the decomposition of acetaldehyde was the bridged carbonyl species. Spectrum 3d indicates that the presence of potassium ions poisoned, to some extent, the decomposition of acetaldehyde (reduced to 54%) and eliminated the

formation of CH_4 and acetone. Most likely the potassium ions cause the formation of inactive carbon at the expense of the active carbon surface species which normally yield hydrocarbon and oxygenated products.

Figure 4 shows that the decomposition of acetaldehyde over 2.2% Rh/Al_2O_3 again produced CH_4, although very little CO_2 or CO, surface acetate, and acetone. Spectrum 4e indicates that the acetate species was primarily confined to the Al_2O_3 support. Again potassium ions (spectrum 4d) poisoned the production of CH_4 and acetone. The most interesting feature appears in spectrum 4b. Upon initial heating at 440 K, twin adsorbed CO bands occurred at 2012 and 2082 cm^{-1}. It is well known[16] that the presence of sharp twin bands which grow and decline in intensity together in this region of the spectrum are indicative of the presence of a rhodium gem dicarbonyl species. However, it is also a fact that these twin bands generally appear at ca. 2030 and 2100 cm^{-1} and refer to a highly dispersed Rh^+ gem dicarbonyl.[16] The gem dicarbonyl bands in spectrum 4b which do grow proportionately appear 18 cm^{-1} lower which could very well mean that acetaldehyde decomposes over Rh/Al_2O_3 to yield a rhodium gem dicarbonyl species with Rh in a zero oxidation state. If so, to our knowledge, this is the first infrared data which has been interpreted as evidence for the existence of a metallic Rh gem dicarbonyl species. Yates and Cavanagh also observed abnormally low frequency infrared bands (2021 and 2088 cm^{-1}) for a Rh gem dicarbonyl species during the decomposition of formaldehyde over 2.2% Rh/Al_2O_3, but they attributed the low frequency of the bands as being due to support perturbation of the CO modes by the presence of oxide-bound species derived from H_2CO.[22] It is possible that the Rh gem dicarbonyl species produced from H_2CO also involved metallic rhodium rather than the usual Rh^+.

Finally, a study of acetone decomposition over 2.2% Rh/TiO$_2$ and 2.2% Rh/Al$_2$O$_3$ was also performed here. However, the results were not inspiring. The infrared bands for gas-phase acetone disappeared, and GC indicated complete decomposition, upon heating at 440 K, but no adsorbed CO species or any other products could be detected by infrared. It would thus appear that acetone decomposes to inactive carbon over supported rhodium.

Conclusions

From this study it may be concluded that: (1) methanol decomposes over supported Rh at 440 K to produce methane if TiO_2 is the support or dimethyl ether if Al_2O_3 is the support; (2) acetaldehyde decomposes over supported Rh at 440 K to produce methane and acetone; (3) acetone decomposes over supported Rh at 440 K to produce inactive carbon only; (4) potassium ions poison the formation of all products by presumably causing the production of large amounts of inactive carbon on the surface; and (5) the new Rh gem dicarbonyl state produced during the decomposition of acetaldehyde over 2.2% Rh/Al_2O_3 probably refers to metallic rhodium rather than the usual Rh^+ species.

References

(1) For example, see Henderson, M.A.; Worley, S.D. J. Phys. Chem. 1985, 89, 1417, and the numerous references quoted therein.

(2) Dai, C.H.; Worley, S.D., J. Phys. Chem. 1986, 90, 4219; Worley, S.D.; Dai, C.H. ACS Symp. Ser. on Catalytic Activation of Carbon Dioxide, ed. W.M. Ayers, in press.

(3) Henderson, M.A.; Worley, S.D. J. Phys. Chem. 1985, 89, 392.

(4) Worley, S.D.; Mattson, G.A.; and Caudill, R. J. Phys. Chem. 1983, 87, 1671.

(5) Solymosi, F.; Erdohelyi, A; Kocsis, M. J. Catal. 1980, 65, 428.

(6) Solymosi, F.; Erdohelyi, A.; Bansagi, T. J. Chem. Soc. Faraday Trans. 1 1981, 77, 2645.

(7) Solymosi, F.; Lancz, M. J. Chem. Soc. Faraday Trans. 1 1986, 82, 883.

(8) Solymosi, F.; Pasztor, M. J. Catal. 1987, 104, 312.

(9) Solymosi, F.; Berko, A.; Tarnoczi, T.I. Surf. Sci. 1984, 141, 533.

(10) Greenler, R.G. J. Chem. Phys. 1962, 37, 2094.

(11) Carrizosa, I.; Munuera, G.; Castanar, S. J. Catal. 1977, 49, 265.

(12) Busca, G.; Rossi, P.F.; Lorenzelli, V.; Benaissa, M.; Travert, J.; Lavalley, J.C. J. Phys. Chem. 1985, 89, 5433.

(13) Lamotte, J.; Saur, O.; Lavalley, J.C.; Busca, G.; Rossi, P.F.; Lorenzelli, V. J. Chem. Soc. Faraday Trans. 1 1986, 82, 3019.

(14)   Busca, G.; Forzatti, P.; Lavalley, J.C.; Tronconi, E. in <u>Catalysis by</u> <u>Acids</u> <u>and</u> <u>Bases</u>, ed. B. Imelik, Elsevier Sci. Pub., Amsterdam, 1985, 15.

(15)   Falk, M.; Whalley, E. J. <u>Chem</u>. <u>Phys</u>. **1961**, <u>34</u>, 1554.

(16)   Rice, C.A.; Worley, S.D.; Curtis, C.W.; Guin, J.A.; Tarrer, A. R. J. <u>Chem</u>. <u>Phys</u>. **1981**, <u>74</u> 6487 and the numerous references quoted therein.

(17)   Worley, S.D.; Rice, C.A.; Mattson, G.A.; Curtis, C.W.; Guin, J.A.; Tarrer, A.R. J. <u>Phys</u>. <u>Chem</u>. **1982**, <u>86</u>, 2714.

(18)   Kiss, J.T.; Gonzalez, R.D. J. <u>Phys</u>. <u>Chem</u>. **1984**, <u>88</u>, 898.

(19)   Van't Bilk, H.F.J.; Van Zon, J.B.A.D.; Huizinga, T.; Vis, J.C.; Koningsberger, D.C.; Prins, R.J. J. Phys. Chem. **1983**, <u>87</u>, 2264.

(20)   Solymosi, F.; Pasztor, M. J. <u>Phys</u>. <u>Chem</u>. **1985**, <u>89</u>, 4789 and the numerous references quoted therein.

(21)   Orita, H.; Shuichi, N.; Tamaru, K. J. <u>Catal</u>. **1984**, <u>90</u>, 183.

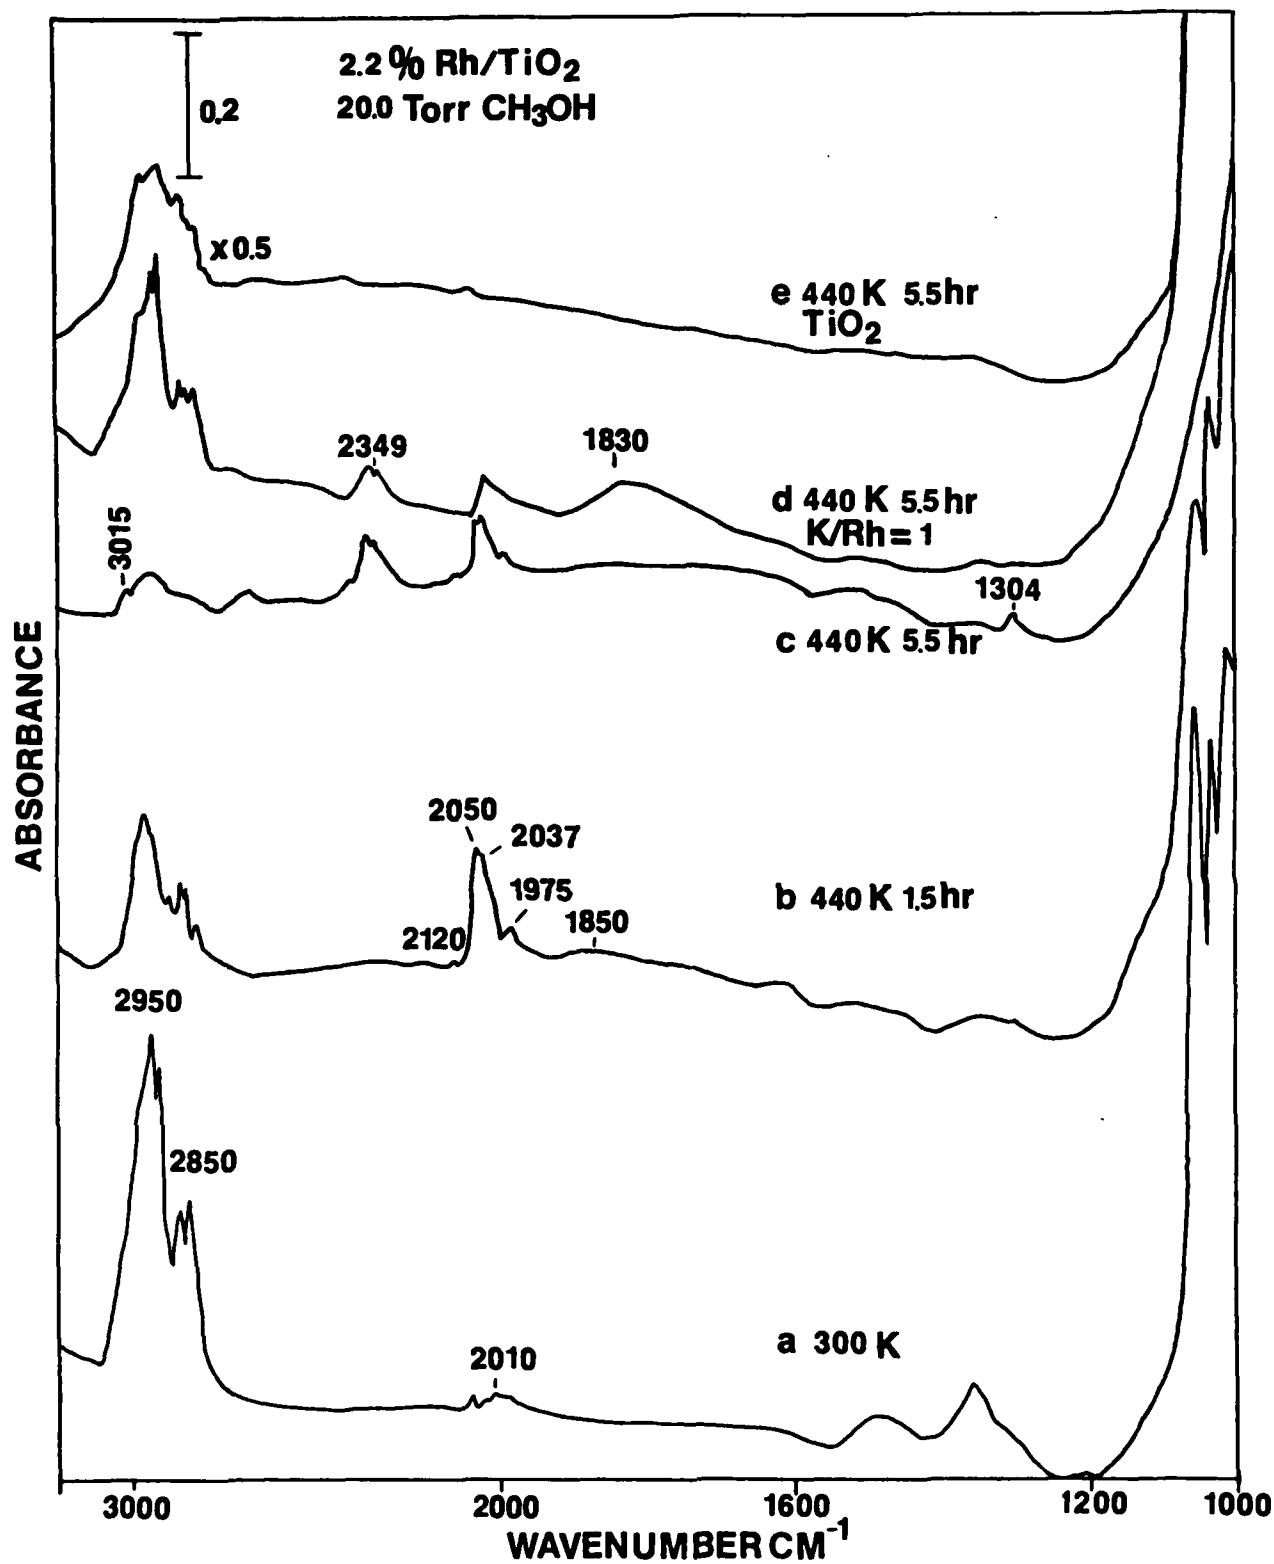(22)   Yates, J.T.; Cavanagh, R.R. J. <u>Catal</u>. **1982**, <u>74</u>, 97.
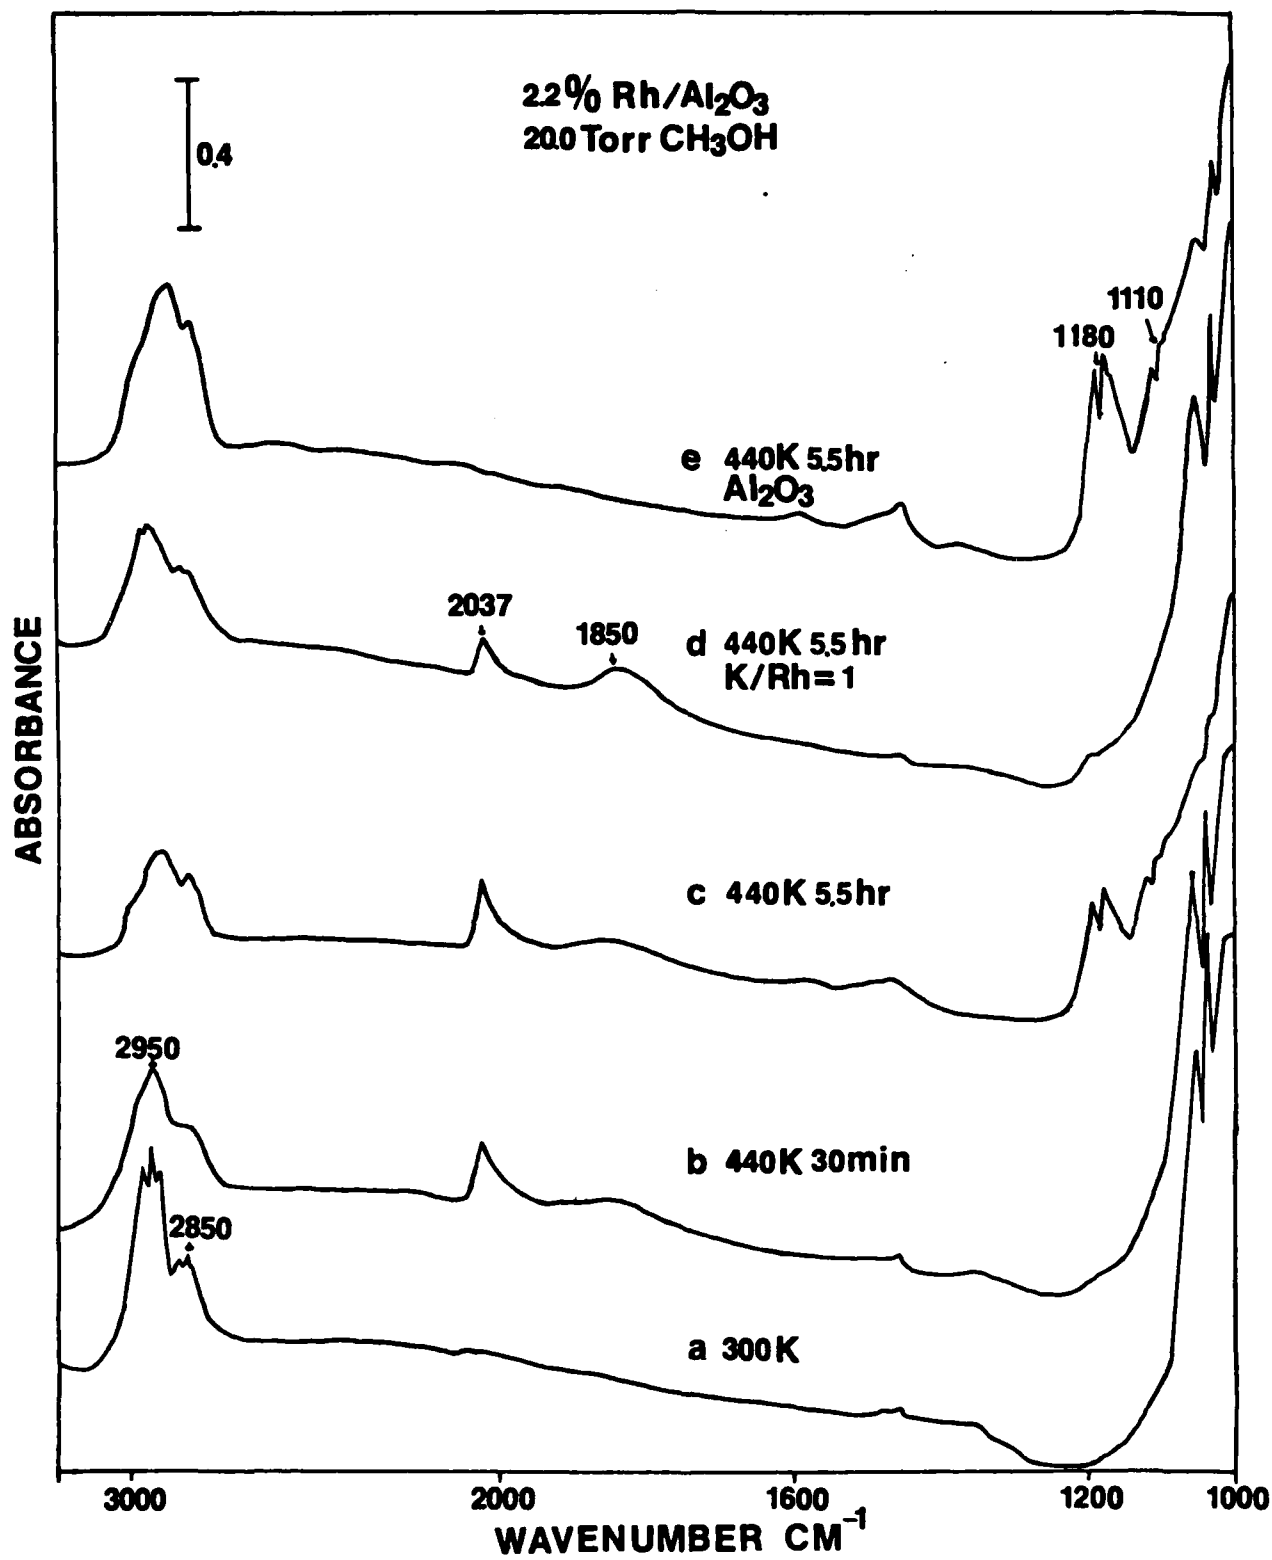
Figure Captions

Figure 1. Infrared spectra for the decomposition of 20.0 Torr methanol over: (a, b, c) a 2.2% Rh/TiO_2 film (4.3 mg cm^{-2}); (d) a 2.2% Rh/TiO_2 film containing K^+; (e) a TiO_2 film.

Figure 2. Infrared spectra for the decomposition of 20.0 Torr methanol over: (a, b, c) a 2.2% Rh/Al_2O_3 film (4.3 mg cm^{-2}); (d) a 2.2% Rh/Al_2O_3 film containing K^+; (e) an Al_2O_3 film.

Figure 3. Infrared spectra for the decomposition of 20.0 Torr acetaldehyde over: (a, b, c) a 2.2% Rh/TiO_2 film (4.3 mg cm^{-2}); (d) a 2.2% Rh/TiO_2 film containing K^+; (e) a TiO_2 film.
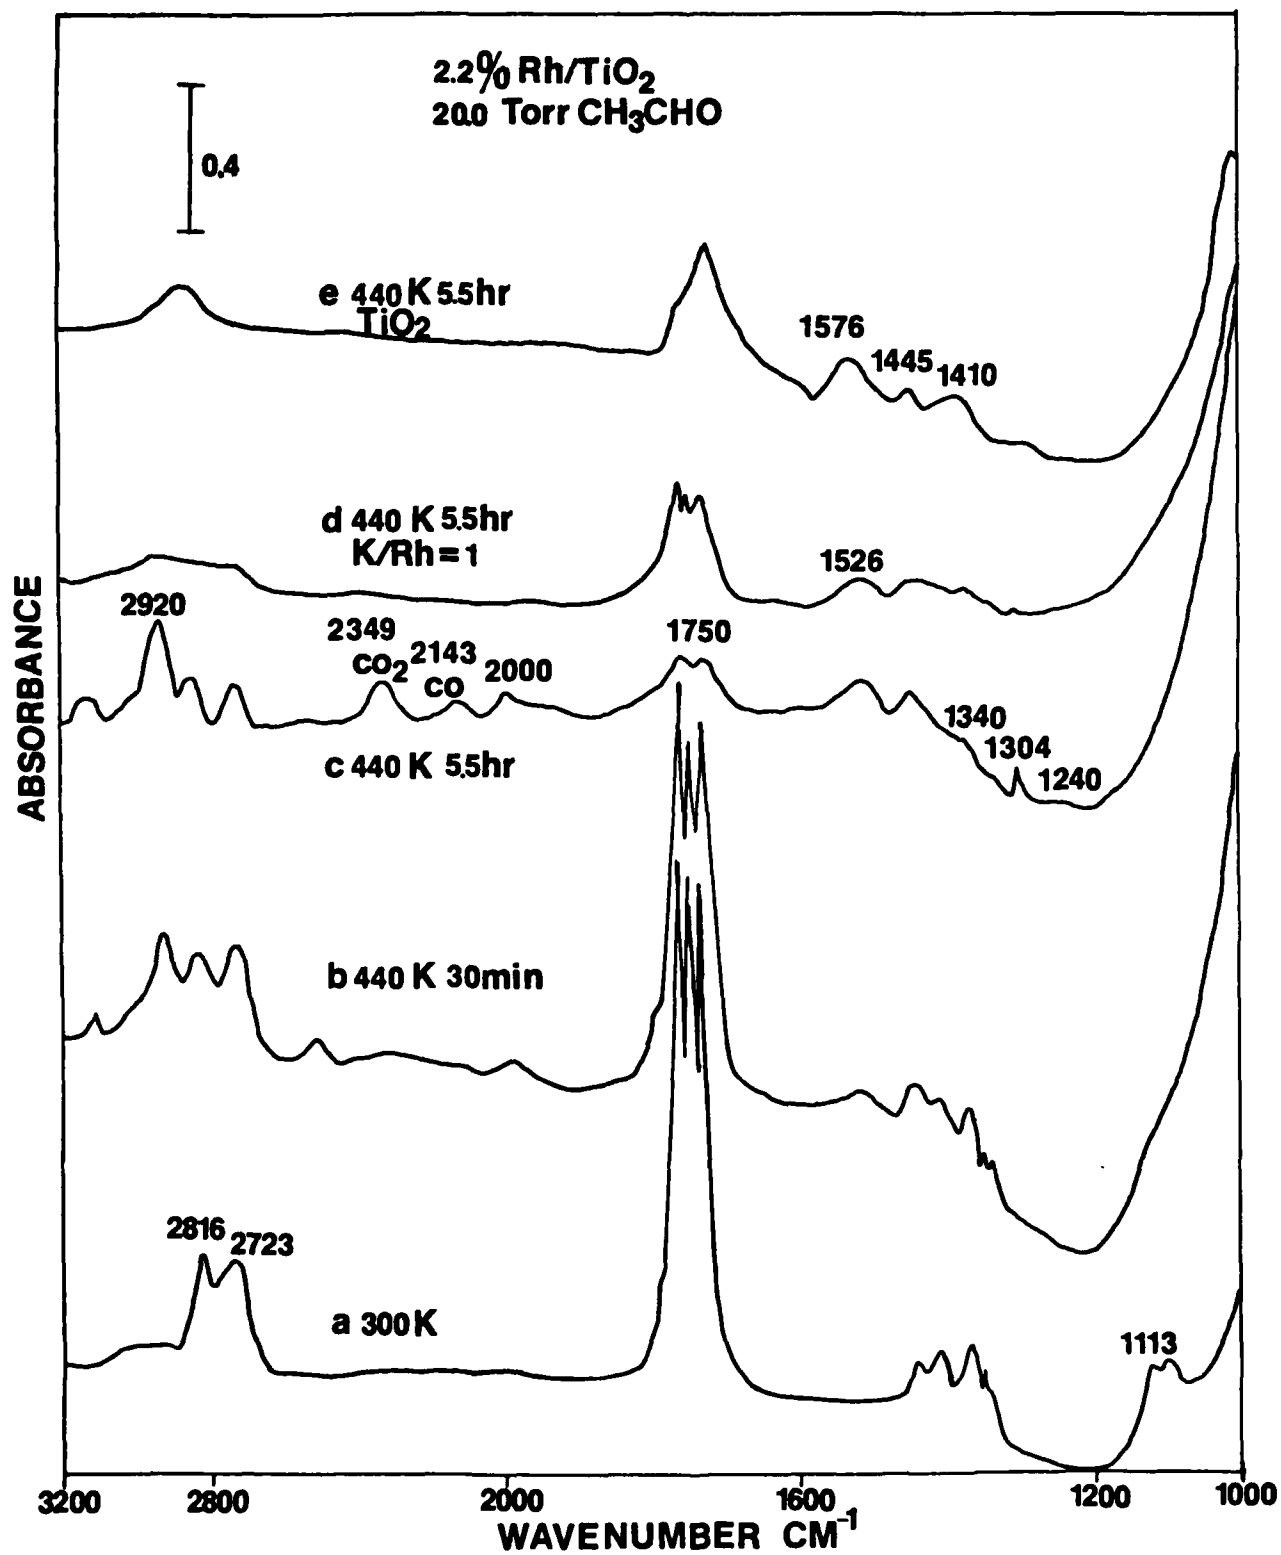
Figure 4. Infrared spectra for the decomposition of 20.0 Torr acetaldehyde over: (a, b, c) a 2.2% Rh/Al_2O_3 film (4.3 mg cm^{-2}); (d) a 2.2% Rh/Al_2O_3 film containing K^+; (e) an Al_2O_3 film.

2.2 % Rh/TiO₂
20.0 Torr CH₃OH

Figure 2.

Worley/Yen
Fig. 3

2.2% Rh/Al$_2$O$_3$
20.0 Torr CH$_3$CHO

e 440K 5.5hr
   Al$_2$O$_3$

1570   1467
         1420

d 440K 5.5hr
   K/Rh=1

c 440K 5.5hr

3015

1350
1304 1220

b 440K 30min

2082   2012

a 300K

ABSORBANCE

04

WAVENUMBER CM^{-1}

3200   2800   2000   1600   1200   1000

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	No. Copies		No. Copies
Office of Naval Research Attn: Code 413 800 N. Quincy Street Arlington, Virginia 22217	2	Dr. David Young Code 334 NORDA NSTL, Mississippi 39529	1
Dr. Bernard Douda Naval Weapons Support Center Code 5042 Crane, Indiana 47522	1	Naval Weapons Center Attn: Dr. A. B. Amster Chemistry Division China Lake, California 93555	1
Commander, Naval Air Systems Command Attn: Code 310C (H. Rosenwasser) Washington, D.C. 20360	1	Scientific Advisor Commandant of the Marine Corps Code RD-1 Washington, D.C. 20380	1
Naval Civil Engineering Laboratory Attn: Dr. R. W. Drisko Port Hueneme, California 93401	1	U.S. Army Research Office Attn: CRD-AA-IP P.O. Box 12211 Research Triangle Park, NC 27709	1
Defense Technical Information Center Building 5, Cameron Station Alexandria, Virginia 22314	12	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, Pennsylvania 19112	1
DTNSRDC Attn: Dr. G. Bosmajian Applied Chemistry Division Annapolis, Maryland 21401	1	Naval Ocean Systems Center Attn: Dr. S. Yamamoto Marine Sciences Division San Diego, California 91232	1
Dr. William Tolles Superintendent Chemistry Division, Code 6100 Naval Research Laboratory Washington, D.C. 20375	1		

ABSTRACTS DISTRIBUTION LIST, 634

Dr. K. N. Nicholas
Department of Chemistry
University of Oklahoma
Norman, Oklahoma   73019

Dr. Aaron Fletcher
Code 3852
Naval Weapons Center
China Lake, California   93555

Dr. A. Wold
Department of Chemistry
Brown University
Providence, Rhode Island   02912

Dr. J. Cooper
Code 6130
Naval Research Laboratory
Washington, D.C.   20375

Dr. M. C. Baird
Department of Chemistry
Queen's University
Kingston, Canada
K7L 3N6

Dr. N. N. Lichtin
Department of Chemistry
Boston University
685 Commonwealth Avenue
Boston, Massachusetts   02215

Dr. R. Eisenberg
Department of Chemistry
University of Rochester
Rochester, New York   14627

Dr. N. Cooper
Department of Chemistry
Harvard University
Cambridge, Massachusetts   02138

Dr. S. D. Worley
Department of Chemistry
Auburn University
Auburn, Alabama   36830

Dr. L. Vaska
Department of Chemistry
Clarkson College
Potsdam, New York   13676

Dr. R. A. Huggins
Materials Science and
   Engineering Department
Stanford University
Stanford, California   94305

END

11-87

DTIC